

STRUCTURAL AND FERROELECTRIC PROPERTIES OF $\text{K}(\text{Nb}_{0.8}\text{Mg}_{0.2})\text{O}_{2.4}\text{F}_{0.6}$ CERAMICS

Taïbi-Benziada L.

Faculty of Chemistry, U.S.T.H.B., P.O. Box 32 El-Alia, 16024 Bab-Ezzouar, Algiers, Algeria.


E-mail: ikra@wissal.dz ; Fax: 213 21 24 73 11

Ferroelectrics ABO_3 with the perovskite-type structure and their solid solutions are of considerable importance for technological applications [1-3]. Nowadays, ABO_3 ceramics become the "heart" of smart systems in many electronic devices with high level of intelligence. Up to now, lead-containing materials such as PbTiO_3 , $\text{Pb}(\text{Zr,Ti})\text{O}_3$ or PZT and $\text{Pb}(\text{Mg,Nb})\text{O}_3$ or PMN have dominated the market of electronics [4, 5]. Nevertheless, lead (Pb) is known to be toxic and may seriously affect human health and natural environment. Therefore, extensive research is actually oriented towards the replacement of lead-based ceramics with lead-free materials. Alkaline niobates and, in particular, potassium niobate KNbO_3 and its solid solutions have been found to be the most promising lead-free ferroelectric compounds [6, 7]. In this study, we report the effect of 20 mol. % of KMgF_3 on the structural and ferroelectric properties of KNbO_3 .

KNbO_3 and KMgF_3 powders were prepared by solid state reaction at 850 and 700 °C, respectively. 80 mol. % of KNbO_3 were then mixed with 20 mol. % of KMgF_3 and dry-ground in a glove box. This powder mixture was pressed into pellets and the tablets were sintered at 900 °C for 15 h in gold sealed tubes under dry helium. The obtained oxifluoride $\text{K}(\text{Nb}_{0.8}\text{Mg}_{0.2})\text{O}_{2.4}\text{F}_{0.6}$ was investigated by X-ray diffraction (XRD), differential scanning calorimetry (DSC) and dielectric measurements performed in a wide temperature range (200-800 K).

Like KNbO_3 , the prepared oxifluoride is orthorhombic at room temperature and undergoes three phase transitions corresponding to various structural changes. These ones occur at $T_1 = 293$ K, $T_2 = 448$ K and $T_C = 544$ K, respectively. The ferroelectric Curie temperature of the fluorinated ceramic ($T_C = 544$ K) is much lower than that of pure potassium niobate ($T_C = 708$ K). A maximum of the dielectric permittivity ϵ of about 1800 and a

dissipation factor $\tan\delta$ of 43 % are observed at T_C . The ceramic $\text{K}(\text{Nb}_{0.8}\text{Mg}_{0.2})\text{O}_{2.4}\text{F}_{0.6}$ could be of interest for electromechanical conversion in piezoelectric devices owing to its high values of T_C and $\tan\delta$.

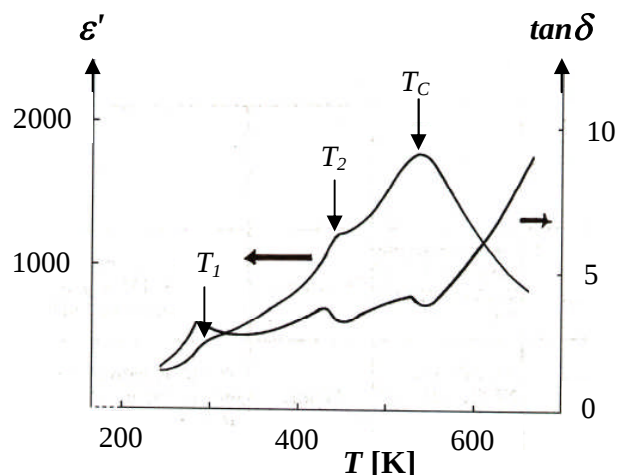

References

- [1] Buchal C., Siebert M., Integr. Ferroelectrics, 35 (2001), 1-10.
- [2] Yoon D.H., Lee B.I., J. Eur. Ceram. Soc., 24 (2004), 753-761.
- [3] Scott J.F., Mater. Sci. Eng., B 120 (2005), 6-12.
- [4] Chu S.Y., Chen T.Y., IEEE Trans. Ultras. Ferroelectri. Freq. Contr., 51 (2004), 663-667.
- [5] Harris N.R., Hill M., Torah R., Townsend R., Beeby S.P., White N.M., Ding G., Sensors and Actuators, A 132 (2006), 311-316.
- [6] Singh K., Lingwal V., Bhatt S.C., Panwar N.S., Semwal B.S., Materials Research Bulletin, 36 (2001), 2365-2374.
- [7] Ringaard E., Wurlitzer T., J. Eur. Ceram. Soc., 25 (2005), 2701-2706.

International Conference HighMatTech, KIEV, Ukraine, 19-23 October 2009.